



Optical and Electrical Properties of Semiconducting ZnS Thin Film Prepared by Chemical Bath Deposition Technique

Joseph Onyeka Emegha^{1*}, Eyetan Dennis Elete², Frank Ochuko-Oghene Efe³,
and Adebowale Clement Adebisi³

¹Department of Physics, University of Benin, Edo State, Nigeria.

²Department of Physics, Federal University of Petroleum Resources, Effurun, Delta State, Nigeria.

³Department of Physics and Engineering Physics, Obafemi Awolowo University, Ile-Ife, Osun State, Nigeria.

Authors' contributions

This work was carried out in collaboration among all authors. Authors JOE and EDE designed the study, performed the statistical analysis, wrote the protocol and wrote the first draft of the manuscript. Authors ACA and EDE managed the analyses of the study. Author FOOE managed the literature searches. All authors read and approved the final manuscript.

Article Information

Editor(s):

(1) Dr. Chong Leong, Gan, SMIEEE, FIET, SMIEEE, RACI CChem, Malaysia.

Reviewers:

(1) A. Ayeshamariam, Khadir Mohideen College, India.

(2) Der-Yuh Lin, National Changhua University of Education, Taiwan.

(3) Adel H. Phillips, Ain-Shams University, Egypt.

Complete Peer review History: <http://www.sdiarticle3.com/review-history/51322>

Original Research Article

Received 27 June 2019
Accepted 02 September 2019
Published 11 September 2019

ABSTRACT

The main purpose of this study is to synthesize and investigate the optical and electrical properties of zinc sulphide (ZnS) thin film which has some interesting optoelectronic properties. The films were grown by chemical bath deposition (CBD) technique on clean soda-lime substrates at room temperature (300K). The films were characterized using Fourier transform infrared spectroscopy (FTIR), Ultraviolet-Visible spectroscopy (UV-Vis), and Four point probe measurements. The FTIR spectrum of the film revealed the characteristic ZnS absorption bands below 800 cm^{-1} . The optical properties were studied in the spectra range of 300 to 1500 nm. The film revealed an average transmittance of above 80% in the visible and near infrared regions with a band gap of 3.30 eV. Optical constants of refractive index, extinction coefficient, electrical susceptibility, dielectric loss

*Corresponding author: Email: jjjemegha@yahoo.com;

were estimated at $\lambda = 800$ nm. The values of $1.25 \Omega \cdot \text{cm}$ and $8.0 \times 10^{-1} (\Omega \cdot \text{cm})^{-1}$ were obtained as the electrical resistivity and conductivity respectively. The determined properties categorize ZnS thin film as a promising material for various optoelectronic devices.

Keywords: Thin films; electrical susceptibility; dielectric loss; electrical resistivity; spectroscopy.

1. INTRODUCTION

Semiconducting materials like zinc sulphide (ZnS) thin films have attracted the attention of many researchers due to their potential application in different field of science and technology. Zinc sulphide as a group II-VI semiconducting material has properties such as direct electronic transition, large band gap, abundance in nature and never toxic [1,2]. Consequently, it finds application in devices such as light emitting diodes, solar cells, anti-reflective coatings, electro-luminescence displays, multilayers dielectric filters, sensor, lasers, and catalysis [3,4].

In recent years, a great deal of interest has been given to the investigation of the properties (optical and electrical) of ZnS thin films in order to finding new device applications and also improve on the performance of the established ones [5]. The properties of ZnS are function of the deposition parameters and the techniques applied. Therefore, investigating the properties of the film with respect to the different deposition technique is a matter of high importance.

ZnS thin films have been prepared by different techniques which include chemical spray pyrolysis, sputtering, metal organic chemical vapour deposition technique, sol-gel chemical technique, electron beam evaporation, molecular beam epitaxy, electrostatic assisted aerosol jet deposition and chemical bath deposition [6-8]. Among these different ZnS thin film deposition techniques mentioned above, chemical bath deposition technique is one of the most attractive form of thin film deposition methods due to its ease of growing films with non-sophisticated materials and equipment, large area deposition and technically straight forward [9,10]. Since chemical bath deposition is a low temperature deposition processes, better orientation of crystallites with improved grain structure is achieved by controlling the deposition parameters [11]. In view of this, an effort has been made to deposit and characterize ZnS thin films using chemical bath deposition technique (CBD).

2. EXPERIMENTATION

Substrates cleaning are important part of thin films deposition process. Commercially available soda-lime substrates used for the study were soak in Acqua Regia for about 50 minutes and then watched thoroughly with detergent. Finally, the substrates were dried with acetone and stored in a hot oven set at 50°C . ZnS thin films were prepared on clean soda-lime substrates using chemical bath deposition (CBD) at room temperature. The reaction bath consist of zinc acetate and thiourea as the sources of the metal (Zn^{2+}) ion and sulphide (S^{2-}) ion respectively, ammonia solution, distilled water and complexing agents. Triethanolamine (TEA) was used to slow down the reaction and avoid precipitates. Distilled water was carefully added to make a total volume of 50ml. The mixtures were carefully stirred to maintain homogeneity with a constant pH kept at 9.0. The substrates were vertically placed inside the vessel with the help of a locally designed substrate holder. After a time period of 24 hours, the substrates were removed from the bath and washed with distilled water and dried in air.

The resultant films were subjected to characterization studies. The chemical properties were examined using Fourier transform infrared (FTIR) spectroscopy. FTIR spectrum of the powder sample was analyzed using Shimadzu 8400 FTIR Spectrophotometer. The spectrum was obtain using pellets of the prepared powder sample in potassium bromide (KBr) background in the range of wavelength $4000 - 400 \text{ cm}^{-1}$. To study the electronic interaction of the deposited film, UV-Vis measurements were performed using a Janway 6405 UV-Vis Spectrophotometer in the range of 300 to 1500 nm. While the electrical properties were investigated using Old Jandel (TY242MP) four point probe technique. The set-up was made in such a way that the voltages (V) across the film and the corresponding currents (I) were measured using a silver paste to ensure electrical contact.

3. RESULTS AND DISCUSSION

3.1 FTIR Spectroscopic Study

The FTIR characterization was undertaken to determine the formation of ZnS and associated functional groups present on the surface of the sample. Fig. 1 shows the FTIR spectrum of ZnS powder in KBr background. An examination of the spectrum showed that the powder exhibits the basic absorption frequency bands between 4000 and 400cm⁻¹. The band observed at 3431cm⁻¹ corresponds to the O-H group emanating from water [12]. Other bands include; a very small peak for N-H at 3257cm⁻¹; C-H vibration between 2918 and 2854 cm⁻¹. The regions between 2353 and 1867 cm⁻¹ consist of C≡C vibration, C=O vibration is seen at 1138cm⁻¹, C-C stretching vibration at 997 cm⁻¹. Zn-S band was observed below 800cm⁻¹. The peaks matched well with those of ZnS thin film spectrum reported in literature [13,14].

3.2 Optical Characterization

The optical measurement constitutes the most direct approach for determining the band structure of ZnS thin films. The Ultraviolet-visible spectrophotometer gave the absorbance of the film as a function of wavelength.. Thus the absorption coefficient (α) is evaluated using the relation [15].

$$\alpha = \frac{1}{W} \ln \frac{1}{T} \tag{1}$$

where W is the thickness of the film whose value is 308 nm, T is the transmittance and it is estimated using the equation [16].

$$T = 10^{-A} \tag{2}$$

The transmittance spectrum in Fig. 2 shows an increase in transmittance with wavelength, and this is in agreement with the observations made by Ikhioya and Agobi [16] and Ebrahimi *et al.*[17]. Also it has been observed that below 500 nm, there is a sharp fall in the transmittance of the film which is due to the strong absorbance of the film in this region [10]. The film shows low transmittance in the UV region which increased with increasing wavelength towards the Visible and near infrared regions of the electromagnetic spectrum. The relatively lower transmittance in the UV region exhibited by the film suggests that ZnS thin film can be exploited for possible application in screening off harmful UV portion of the electromagnetic spectrum which is detrimental to both animals and humans health [11]. The observed high transmittance in the visible and near infrared regions makes the film a useful material for solar cells and pyro-electric detection [9,16].

The absorption coefficient of ZnS thin film has been observed to obey the exponential relation [18];

$$\alpha = \frac{B}{hv} [hv - Eg]^m \tag{3}$$



Fig. 1. FTIR spectrum of ZnS powder

where B is a constant, E_g is the optical band gap energy and the index m can be any value between $\frac{1}{2}$ and 3 depending on the nature of the inter-band electronic transition. It has been established that for ZnS as a direct allowed band gap semiconductor, the exponent in Equation 3 fits well for $m = \frac{1}{2}$ [4], Therefore;

$$\alpha = \frac{B}{hv} [hv - E_g]^{1/2} \tag{4}$$

Fig. 3. shows the plot of the square of the absorption coefficient against photon energy which was accomplished using Equation 4. The band gap value of the deposited film was determined by extrapolating the linear portion of the graph to zero. As can be seen from the figure, the band gap energy is equal to 3.30 eV. This result agrees with several studies on semiconducting ZnS thin films obtained in literature [2,4,6].

The refractive index (n) and extinction coefficient (k) are two fundamental properties of an optical material due to the close relationship with the electronic polarization of the ions [19]. So, determining these properties of a semiconducting material is important for potential applications in optoelectronics device like switches, filters and modulators. etc [19,20]. The refractive index (n) of a material could be obtained from the corrected reflectance (R) data using a computational method [21];

$$n = - \frac{(R+1) \pm \sqrt{3R^2+10R-3}}{2(R-1)} \tag{5}$$

The value of the refractive index (n) was 2.04 at $\lambda = 800$ nm. The range of the refractive index makes ZnS film suitable for use in optoelectronic devices.

The extinction coefficient (k) of the material could be calculated using the following equation,

$$k = \frac{\alpha\lambda}{(4\pi)} \tag{6}$$

Here, α is the absorption coefficient of the material. The extinction coefficient (k) was found to be 0.0092 at $\lambda = 800$ nm.

From the classical theory of dielectric materials, the electrical susceptibility (X_e) which determines the polarization of a material with respect to applied electric field is estimated using the relation;

$$X_e = \epsilon - 1 \tag{7}$$

Where ϵ is the dielectric constant of the material. Also from Naseem, 2010. [22];

$$n = \sqrt{\epsilon} \tag{8}$$

hence, we have

$$X_e = n^2 - 1 \tag{9}$$

when n is the refractive index, the value of the electrical susceptibility is equal to 3.16 at $\lambda = 800$

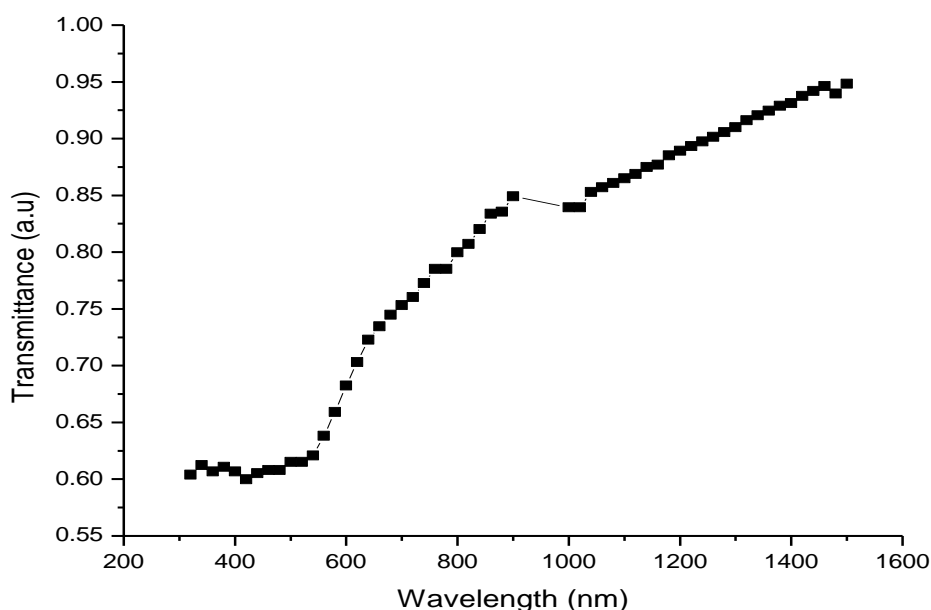


Fig. 2. Transmittance versus wavelength of ZnS thin film

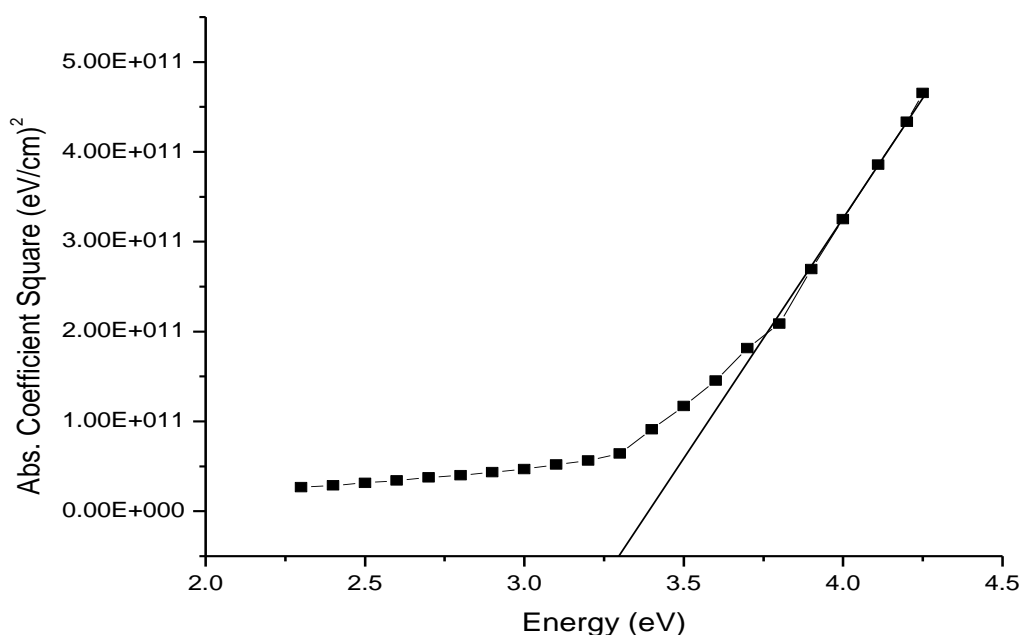


Fig. 3. The plot of square of Abs. coefficient versus energy for ZnS thin film

nm. Since the value of X_e is greater than 1, the material can easily be polarized in response to the field therefore, reducing the stored energy within the film [21].

It is well known that the dielectric constant (ϵ) of a material is directly related to the density of states within the energy gap and depends on the electronic structure of the material. It is fundamentally an intrinsic property of a material that is express as follows;

$$\epsilon = \epsilon_r + \epsilon_i \tag{10}$$

where ϵ_r and ϵ_i are the real and imaginary part of the dielectric constant. The real part ϵ_r is associated with the speed of light in the material while the imaginary part ϵ_i is concern with the energy absorption due to dipole motion from the field [23]. The real (ϵ_r) and the imaginary (ϵ_i) part of the dielectric constant could be estimated using the following expressions

$$\epsilon_r = n^2 - k^2 \tag{11}$$

$$\epsilon_i = 2\pi k \tag{12}$$

The values of the real and imaginary dielectric constant at $\lambda = 800$ nm were 3.699 and 0.0028 respectively. The values of the dielectric complex are capable of inducing polarization from the electromagnetic light.

The energy loss is related to the optical properties through the dielectric constant. It is concern with the loss of energy associated with

the heating of the dielectric material in an electric field [23,24]. The dielectric loss was determine using the relations.

$$\tan \Phi = \frac{\epsilon_i}{\epsilon_r} \tag{13}$$

and

$$\text{loss angle } \Phi = \tan^{-1}\left(\frac{\epsilon_i}{\epsilon_r}\right) \tag{14}$$

Therefore dielectric energy loss and the loss angle at $\lambda = 800$ nm were found to be 1.32×10^{-5} and 0.0434 respectively.

3.3 Electrical Properties

The electrical (I-V) analysis of ZnS film was observed using four point probe method. The average current and the corresponding voltage are illustrated in Fig. 4. We observed that the current flowing through the film increases linearly with the voltage of the electrode. This implies higher conductivity of the film which may be helpful in obtaining higher frequency in solar cell fabrication [21]. The average current and voltage were found to be 2.213×10^{-7} A and 19.8×10^{-2} V respectively.

The resistivity (ρ) was estimated using the relation [25];

$$\rho = \frac{\pi}{\ln 2} \left(\frac{V}{I}\right) \times w \tag{15}$$

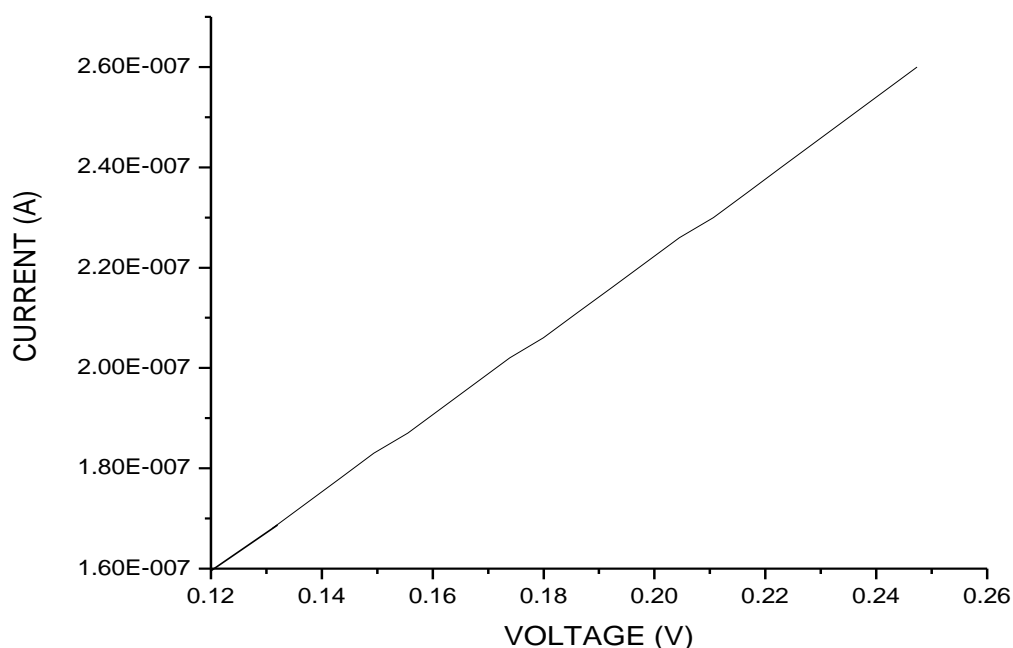


Fig. 4. I-V characteristic of ZnS thin film

Here W is the thickness (308 nm), V and I are the average voltage and current of the film respectively. The reciprocal of the resistivity was taken as the conductivity (σ) of the film.

$$\sigma = \frac{1}{\rho} \quad (16)$$

from the values of resistivity (ρ) and thickness (W), the sheet resistance (R_s) can be determined as

$$R_s = \frac{\rho}{W} \quad (17)$$

The sheet resistance was found to be $4.06 \times 10^6 \Omega/\text{Sq.}$, the resistivity was calculated to be $1.25 \Omega \cdot \text{cm}$ and the conductivity was also calculated to be $8.0 \times 10^{-1} (\Omega \cdot \text{cm})^{-1}$. The electrical conductivity value falls within the magnitude of 10^{-13} to 10^2 reported for semiconducting thin films in literature [3], suggesting that the deposited film is conductive in nature. The observed high resistive value of the film indicates that it could find application as semiconducting sensors.

4. CONCLUSION

Zinc sulphide (ZnS) thin films were prepared by chemical bath deposition technique at room temperature for a period of 24 hours. The deposited films were characterized and the result

showed that the film possesses a high transmittance in the visible and near infrared regions with a band gap of 3.30 eV. The spectrum equally revealed other optical properties such as the refractive index, extinction coefficient, electrical susceptibility and dielectric loss which were analyzed for device applications. The electrical characterization of the film using four point probe measurement gave the values of resistivity and conductivity to be $1.25 \Omega \cdot \text{cm}$ and $8.0 \times 10^{-1} (\Omega \cdot \text{cm})^{-1}$ respectively. The excellent optical and electrical properties of the deposited film make it useful as window materials in thin film technology and applicable in the manufacturing of thin film embedded resistors.

COMPETING INTERESTS

The authors have declared that no competing interests exist.

REFERENCES

1. Bilgin V, Erturk K, Ozutok F. Growth, electrical and optical study of ZnS: Mn thin films. Proceedings of the International Congress on Advance in Applied Physics and Materials Science. 2012;121: 221-223.
2. Saeed NM. Structural and optical properties of ZnS thin films prepared by

- spray pyrolysis technique. Journal of Al-Nahrain University. 2011;14(2):86-92.
3. Okafor PC, Ekpunobi, AJ, Ekwo PA. Effect of manganese percentage doping on thickness and conductivity of zinc sulphide nanofilms prepared by electrodeposition method. International Journal of Science and Research (IJSR). 2014;4: 2275-2279.
 4. Bioki HA, Zarandi MB. Effect of annealing and thickness on the structural and optical properties of crystalline ZnS thin films prepared by PVD method. International Journal of Optics and Photonics (IJOP). 2011;5(2):121-127.
 5. Patidar D, Rathore KS, Saxena NS, Sharma K, Sharma TP. Energy band gap and conductivity measurement of CdSe thin film. Chalcogenide Letters. 2008;5(2): 21-25.
 6. Jasib AA, Yousif AA. The effect of thickness nanoparticle ZnS films on optical properties. International Journal of Basic and Applied Science. 2015;3:38-51.
 7. Osasona S, Djebah A, Ojo IAO, Eleruja MA, Adedeji AV, Jeyne C, Ajayi EOB. Preparation and characterization of MOCVD thin films of zinc sulphide. Optical Materials. 1997;7:109-115.
 8. Mosiori CO, Njoroge WK, Okum John. Electrical properties of zinc sulphide (ZnS) thin films grown by chemical bath deposition. Physical Science Research International. 2015;795-803.
 9. Usoh CI, Okujagu CU. Spectral analysis of amorphous thin films of MnS obtained chemically by varying solution concentrations. Research Journal of Physical Sciences. 2014;2(2):1-8.
 10. Abbas MM, Shehab AA, Al-Samuraee AK, Hassan, NA. Effect of deposition time on the optical characteristics of chemically deposited nanostructure PbS thin films. Energy Procedia. 2011;6:241-250.
 11. Nnabuchi MN, Ekuma CE. Synthesis and characterization of chemically bath deposited CdCoS thin films. Chalcogenide Letters. 2010;7(1):31-38.
 12. Bargir S, Farhadi S. Microwave-assisted rapid synthesis of Co_3O_4 nanorods from $\text{CoC}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$ nanorods and its application in photocatalytic degradation of methylene blue under visible light irradiation. Int. J. Nano Dimens. 2017;8(4):284-297.
 13. Kavitha B, Anitha R, Thangam Y. Novel method to synthesize and characterize zinc sulphide nanoparticle. International Journal of Applied Sciences and Engineering Research. 2012;1:282-286.
 14. Hedayati K, Zndehnam A, Hassanpour F, Fabrication and characterization of zinc sulphide nanoparticle and nanocomposites prepared via a simple chemical precipitation method. J. Nanostruct. 2006; 6:207-212.
 15. Fasakin O, Eleruja MA, Akinwunmi OO, Olofinjana B, Ajenifuja E, Ajayi EOB. Synthesis and characterization of metal organic chemical vapour deposited copper titanium oxide (Cu-Ti-O) thin films from single solid source precursor. Journal of Modern Physics. 2013;4:1-6.
 16. Ikhioya IL, Agobi A. Effect of bath composition on the optical and electrical properties of zinc sulphide (ZnS) thin film using electrodeposition technique. Journal of the Nigerian Association of Mathematical Physics. 2016;33:147-154.
 17. Ebrahimi S, Yarmand B, Naderi N. Optical and electrical properties of ZnS thin films prepared by spray pyrolysis. The 2nd International Conference on Ceramics, Niroom Research Institute, Tehran, IRAN. 2017;16-18.
 18. Emegha JO, Olofinjana B, Eleruja MA, Efe O, Azi SO. Preparation and physical properties of $\text{Cu}_x\text{Zn}_{1-x}\text{S}$ thin films deposited by metal organic chemical vapour deposition technique. Journal of Materials Science Research and Reviews. 2019; 2(4):1-9.
 19. Ahmad S, Ashraf M, Ahmad A, Singh DV. Electronic and optical properties of semiconductor and alkali halides. Arab J. Sci Eng. 2013;38:1889-1894.
 20. Hassanien AS, Akl AA. Influence of composition on optical and dispersion parameters of thermally evaporated non-crystalline $\text{Cd}_{50}\text{S}_{50-x}\text{Se}_x$ thin films. Journal of Alloys and Compounds. 2015;648:280-290.
 21. Thirumavalavan S, Mani K, Sagadevan S. Investigation of the structural, optical and electrical properties of copper selenide thin films. Materials Research. 2015;18(5): 1000-1007.
 22. Naseem A, Computation and analysis of effective permittivity of thin nanostructure: An effective medium perspective. Master

- Thesis. The University of Toledo, USA; 2010.
23. Taskin M, Podder J. Dielectric properties of pure and cobalt doped zinc oxide thin films prepared by spray pyrolysis. Applied Science Reports. 2014;7(3):112-116.
24. Moghadam RZ, Ehsani MH, Rezagholiour Dizaji H, Sazideh MR. Thickness dependence of optical properties of CdTe films. Iranian Journal of Material Science and Engineering. 2018;15(3):21-31.
25. Olofinjana B, Egharevba G, Taleatu B, Akinwunmi O, Ajayi EO. MOCVD of molybdenum sulfide thin film via single solid source precursor bis-(Morpholinodithioato-s,s')-Mo. Journal of Modern Physics. 2011;2:341-349.

© 2019 Emegha et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

*The peer review history for this paper can be accessed here:
<http://www.sdiarticle3.com/review-history/51322>*