

## Biosorption of Metal Ions from Aqueous Solution by Immobilized *Moringa oleifera* Bark

B. J. Tizhe<sup>1</sup>, S. A. Osemeahon<sup>1\*</sup>, I. I. Nkafamiya<sup>1</sup> and M. H. Shagal<sup>1</sup>

<sup>1</sup>Department of Chemistry, Moddibo Adama University of Technology, Yola, Nigeria.

### Authors' contributions

This work was carried out in collaboration between all authors. Author SAO designed the study, performed the statistical analysis, wrote the protocol, and wrote the first draft of the manuscript and managed literature searches. Authors BJT, IIN and MHS managed the analyses of the study and literature searches. All authors read and approved the final manuscript.

### Article Information

DOI: 10.9734/IRJPAC/2015/13712

#### Editor(s):

(1) Edmond Dik-Lung Ma, Department of Chemistry, Hong Kong Baptist University, Hong Kong, China.

#### Reviewers:

(1) Anonymous, Universiti Sains Malaysia, Malaysia.

(2) Gregorio Guadalupe Carbajal Arizaga, Chemistry Department, University of Guadalajara, México.

(3) Eman N. Ali, Faculty of Chemical & Natural Resources Engineering, Universiti Malaysia Pahang, Malaysia.

Complete Peer review History: <http://www.sciencedomain.org/review-history.php?iid=808&id=7&aid=7145>

Original Research Article

Received 30<sup>th</sup> August 2014  
Accepted 3<sup>rd</sup> November 2014  
Published 8<sup>th</sup> December 2014

### ABSTRACT

This study investigated the effectiveness of immobilized *Moringa oleifera* bark (IMOB) for the removal of heavy metal ions from waste water. The concentration of residual metal ion concentration was determined using Atomic Absorption Spectrophotometer (AAS). The immobilization of *Moringa oleifera* (*M. oleifera*) bark was achieved by entrapping it within a polymeric matrix of calcium alginate. The Sorption capacity of 95.43%, 95.51%, 93.67%, was recorded for Zn<sup>2+</sup>, Cd<sup>2+</sup> and Fe<sup>2+</sup> respectively. An increase in sorption capacity was recorded as the pH, contact time and initial metal ion concentration increases, while there was a decrease in sorption capacity as the ionic strength increases. The result of this study present *M. oleifera* bark as a potential biosorbent for the removal of these heavy metal ions from waste water.

**Keywords:** Heavy metals; *Moringa oleifera* bark; biosorption; immobilization.

\*Corresponding author: Email: [sundayosemeahon@yahoo.com](mailto:sundayosemeahon@yahoo.com);

## 1. INTRODUCTION

Water is considered to be a vital and limited resource. Population growth, industrial development and other pressure faced by developing countries have led to structured measures to ensure sustainable management of this important natural resource [1]. Water will continue to be a major issue with definite and profound importance on our live and that of the planet earth [2]. Water contaminated by heavy metal ions has plagued the human race into a recurring hazard world-wide. The presence of these heavy metal ions in waste water has pose an important problem for the environment as well as for the treatment process, because the disposal of both treated water and activated sludge contaminated with heavy metal ions give rise to detrimental impacts on the environment.

In view of the toxicity and in order to meet regulatory discharging standards, it is essential to remove heavy metals from waste water, so as to improve its quality [3]. Conventional methods for the removal of metal ions from wastewater include chemical precipitation, electrolysis, membrane separation, ion exchange and adsorption. Most of these methods are hard to come by, because of the high capital and regeneration cost of the material [4]. In the same vein, advanced water treatment techniques are too costly for many developing nations [5]. Biosorption utilizes inexpensive dead biomass like algae, bacteria, fungi and yeast. Recent studies have also shown that heavy metals can be removed using plant materials such as palm pressed fibers and coconut husk [6], Wheat bran [7] and Yohimbe bark waste [8].

The *M. oleifera* plant is found and cultivated in most parts of Nigeria and much concentration is being focused on the use of its seed, which is presently used for many purposes. However, the full potential of *M. oleifera* is yet to be harnessed. Therefore, the aim of this study is to evaluate the potentials of *M. oleifera* bark as bio-sorbent for removal of heavy metal ions from waste water.

## 2. MATERIALS AND METHODS

Sodium alginate, calcium chloride, sodium hydroxide and hydrochloric acid were obtained from British Drug House (BDH). *M. oleifera* bark was sampled from Ngurore in Yola South Local Government Area of Adamawa state, Nigeria. All materials were used as supplied.

### 2.1 Preparation of *M. oleifera* Bark

The *M. oleifera* bark was sun-dried for 21 days. It was then powdered in a mortar and sieved through 100  $\mu\text{m}$  mesh to produce a fine powder. The sieved material was packed in polyethylene bag for further use. First, 4.0 g of the bark powder was weighed and dissolved in 100  $\text{cm}^3$  of water and left to stand for 12 hours.

### 2.2 Preparation of Sodium Alginate and Calcium Chloride Solution

Sodium alginate was prepared by weighing 4.0 g of sodium alginate and making it up to 100  $\text{cm}^3$  mark in a volumetric flask with distilled water. It was left overnight for complete dissolution to give 4% w/v. Calcium chloride, 0.12 M, was prepared by weighing 13.32 g into 1L flask and made up to mark with distilled water [9].

### 2.3 Immobilization of the *M. oleifera* Bark

50  $\text{cm}^3$  of dissolved *M. oleifera* bark was thoroughly mixed with 50  $\text{cm}^3$  of 4% stock solution of sodium alginate and stirred vigorously for even mixing in a 250  $\text{cm}^3$  beaker. The mixture was subsequently poured into another beaker containing 30  $\text{cm}^3$  of 0.12 M calcium chloride solution. The reaction was allowed retention time of 1 hour for complete precipitation. The precipitated blend solid was then filtered and allowed to dry at room temperature (30°C). The dried solid mass was stored in a polythene bag for further use.

### 2.4 Preparation of the Metal Ions Stock Solution as Synthetic Waste Water

The metal ions chosen for this study are  $\text{Zn}^{2+}$ ,  $\text{Cd}^{2+}$  and  $\text{Fe}^{2+}$ . The stock solution of 1000 ppm was prepared by dissolving 2.10 g and 4.10 g and 3.54 g of zinc nitrate, cadmium nitrate and iron nitrate respectively in 1 litre volumetric flask and made up to the mark. From the stock solution, serial dilution of 200 ppm of each metal ion was prepared in distilled water.

### 2.5 Sorbent (*M. oleifera* Immobilized Bark) Sorption Capacity

From 200 ppm of each metal ion solution, 50  $\text{cm}^3$  was taken into a conical flask (covered with a rubber bung), 0.2 g of dried sample added and then shaken with a flask shaker for two hours. The solution was then filtered and the

concentration of the residual metal ion in the filtrate was determined using Atomic Absorption Spectrophotometer AAS (Model 210 VGP Buck Scientific) [10]. This process was repeated for all metal ions.

## 2.6 Determination of the Effect of pH on Sorption Capacity

The sorption characteristics of the *M. oleifera* immobilized bark at different pH values (1.0 to 6.0) were investigated at 30°C. 1.0 M hydrochloric acid and 1.0 M sodium hydroxide were used to adjust the pH of the solution as the case may be. The residual metal ion was measured as stated above [10].

## 2.7 Determination of the Effect of the Ionic Strength on Sorption Capacity

The ionic strength of the 200 ppm solution was adjusted by dissolving about 0.1 g, 0.5 g, 1.0 g, 1.5 g and 2.0 g of NaCl to obtain 0.1 – 1.0 w/v.

## 2.8 Determination of the Effects of the Contact Time on Sorption Capacity

In order to determine the kinetics of the sorption for the various metal ions, several set of samples consisting of 0.2 g of the dried sorbent and 50 cm<sup>3</sup> of the metal ion solution for each of the ions was prepared. As the samples were undergoing agitation (on the shaker), they were removed one after the other at a predetermined time interval ranging from 0.5 hours to 24 hours for analysis.

The solution was filtered and analysed for residual metal ion. This was done for all metal ions at 30°C.

## 2.9 Determination of the Effect of the Initial Metal Ion concentration on Sorption Capacity

The effect of the initial metal ion concentration on the sorption capacity of different samples consisting of 50 cm<sup>3</sup> each of different metal ion concentrations ranging from 5 ppm – 100 ppm, but each containing 0.2 g of the dried *M. oleifera* bark were prepared and shaken until equilibrium was obtained at 30°C. The synthetic waste water was then filtered and analyzed for residual metal ion concentration.

## 3. RESULTS AND DISCUSSION

### 3.1 Sorption Capacity

The sorption capacity for Zn<sup>2+</sup>, Cd<sup>2+</sup> and Fe<sup>2+</sup> is shown in Fig. 1. The values of 98.43%, 95.51% and 93.67% was recorded for Zn<sup>2+</sup>, Cd<sup>2+</sup> and Fe<sup>2+</sup> respectively. The result from the present study is comparable to the ones reported by [11]. The sorption capacity for different metal ions is due to the ability of the metal ion to form covalent bond with the functional groups in the biomass, the hydration free energy and the nature of the surface sites which provides large pore structure for sorption of the metal ions in the aqueous solution [12].

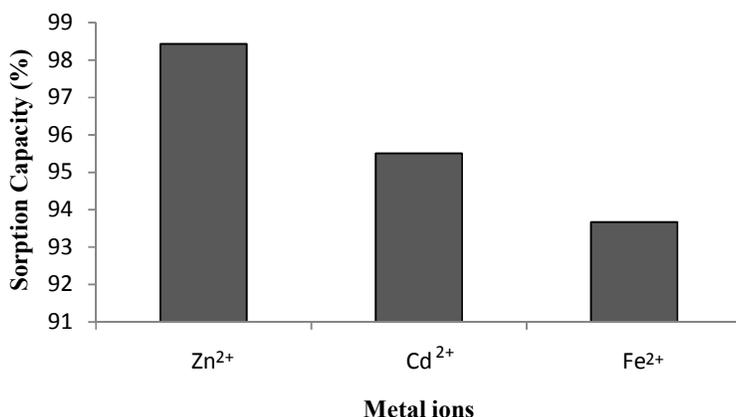


Fig. 1. Sorption capacity of metal ions by IMOB

### 3.2 Effect of Contact Time on Sorption Capacity

The result of sorption studies carried out as a function of contact time for the heavy metal ions is shown in Fig. 2. It shows that the removal of the metal ion by Immobilised *M. oleifera* bark (IMOB) took place in two distinct steps: A relatively quick phase in which rapid sorption was recorded within 2 hours, followed by a slow increase in sorption capacity, until equilibrium was reached. This sorption is due to existence of functional groups in the biomass, which is capable of forming a complex with the metal ions [13,14]. The high rate of sorption is due to the nature of the biosorbent such as surface area, porosity and its available sorption sites [15]. The high rate of sorption (within 2 hours) is desirable both economically and process operations.

### 3.3 Effect of Ionic Strength on Sorption Capacity

The effect of ionic strength on sorption capacity was studied and the result obtained is shown in Fig. 3. It is evident that the sorption capacity decreases as the ionic strength increases.

The reduction in uptake is probably due to the excess of the  $\text{Na}^+$  ions which inhibit the approach of the metal ions to the active sites of the bio sorbent [16]. In the same vein there are two possible ways generally by which increasing the ionic strength can influence metal ion uptake on different biosorbent, firstly by decrease the solution-phase activity of the metal ion and secondly by increase in the concentration of the competing ion ( $\text{Na}^+$ ). The competition for active binding sites between the  $\text{Na}^+$  and metal ions

could also be implicated with respect to the decrease in sorption capacity as the ionic strength increases [17].

### 3.4 Effect of pH on Sorption Capacity

Studies have shown that pH is an important factor affecting biosorption of heavy metals [4,18]. It is well known that pH affects the protonation of the functional groups on the biomass as well as the solution Chemistry.

The influence of pH on Sorption capacity was studied in the range of 1.0 – 6.0. The relationship between the values and the quantities of heavy metals sorbed on IMOB biosorbent is presented in Fig. 4. It can be observed that the sorption capacity increases with increasing pH. This result is due to competition for active sorption sites between the metal ions and Hydrogen ions. An optimum pH value of 4.0 was recorded for  $\text{Zn}^{2+}$  and  $\text{Fe}^{2+}$  respectively, 5.0 for  $\text{Cd}^{2+}$ .

### 3.5 Effect of Initial Concentration on Sorption Capacity

Fig. 5 depicts the effect of initial metal ion concentration on sorption capacity. It is observed that the metal ion uptake increases with increase in initial concentration for all the metal ions studied. The mechanism of metal uptake in particular depends on the initial heavy metal ion concentration, because low concentrations metal ions are absorbed by specific active sites, while with increasing metal ion concentrations the binding sites becomes more quickly saturated as the amount of biomass concentration remained constant [19].

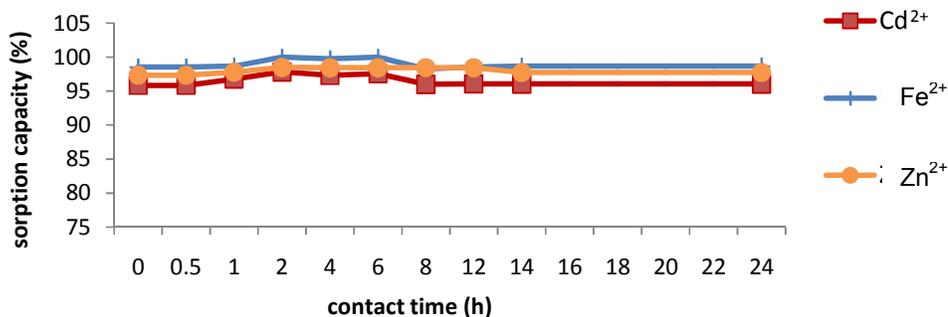


Fig. 2. Effect of contact time on sorption capacity of  $\text{Cd}^{2+}$ ,  $\text{Fe}^{2+}$  and  $\text{Zn}^{2+}$  by IMOB

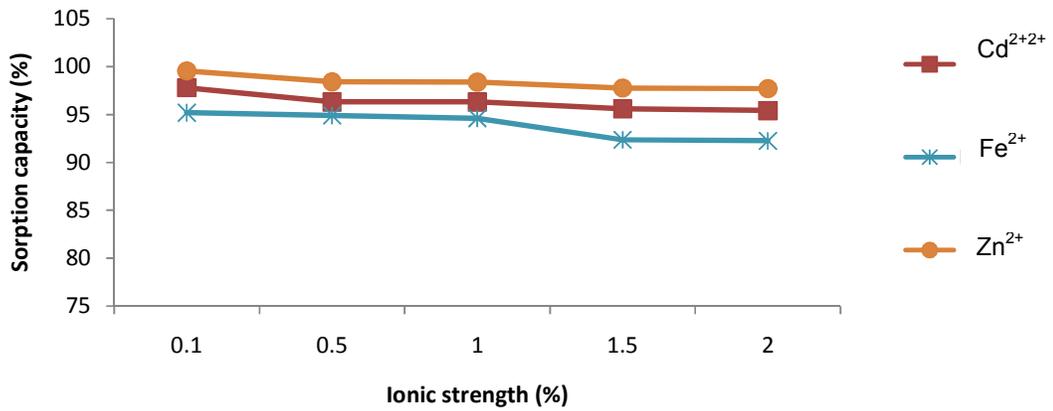


Fig. 3. Effect of ionic strength on sorption of Cd<sup>2+</sup>, Zn<sup>2+</sup> and Fe<sup>2+</sup> by IMOB

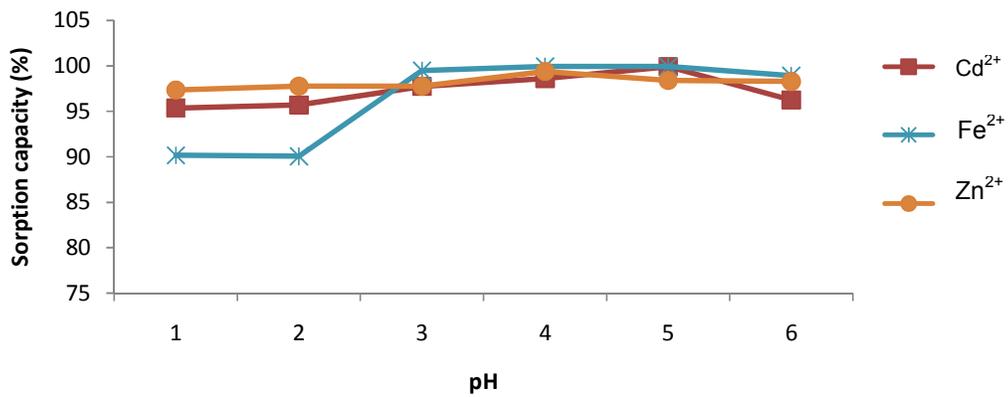


Fig. 4. Effect of pH on sorption of Zn<sup>2+</sup>, Cd<sup>2+</sup> and Fe<sup>2+</sup> by IMOB

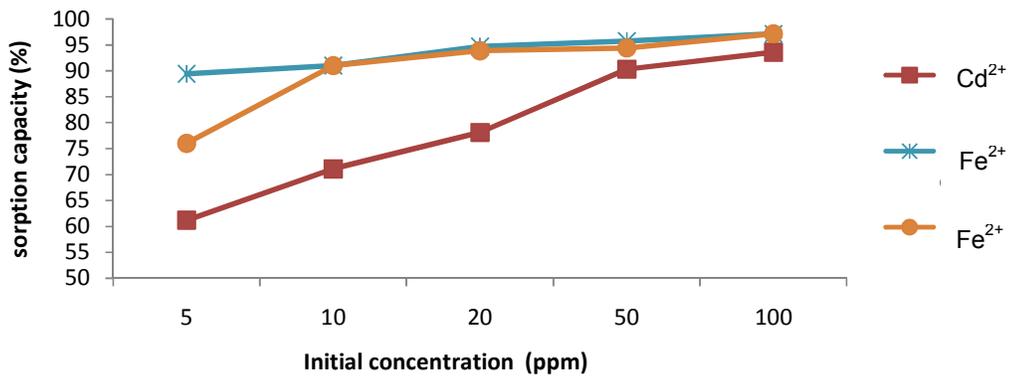


Fig. 5. Effect of initial concentration on sorption of Zn<sup>2+</sup>, Cd<sup>2+</sup> and Fe<sup>2+</sup> by IMOB

The above result can also be explained on the basis of the pore structure, surface area, and existence of a wide spectrum of surface functional groups of the biosorbent.

#### 4. CONCLUSION

This study indicates that *M. oleifera* bark which is widely available in Nigeria at low cost can be used as an efficient biomaterial for the removal of heavy metal ions from waste water. The biosorption was dependent on sorption capacity, contact time, pH, ionic strength and initial metal ion concentration. The potential portrayed by the biomass shows that it can be used as an environmentally friendly technology for wastewater treatment.

#### COMPETING INTERESTS

Authors have declared that no competing interests exist.

#### REFERENCES

- Dobson RS, Burges JE. Biological treatment of precious metal from refinery waste water: A review. *Mineral Eng.* 2007;20:519-532.
- Osemeahon SA, Barminas JT, Aliyu BA, Maina HM. Preliminary evaluation on the application of graft membrane for sorption of copper and lead ions in aqueous solution. *International Journal physical Science.* 2007;2(11):294–299.
- Adedagalla VA, Naif AD, Nidal H. Study of various parameters in the biosorption of heavy metal on activated sludge. *World Applied Sciences Journal.* 2009;5:32–40
- Huang CP, Hung JP, Morehart AL. Removal of Cu (II) from dilute aqueous solutions *Saccharomyces cerevisiae*, *water Res.* 1990;24:433–439.
- Monica C. Elucidation of bactericidal effect incurred by *M. oleifera* and chitosan. *J. US. SJWP.* 2009;4:65-79.
- Tan WT, Ooi ST, Lee CK. Removal of chromium (VI) from solution by coconut husk and palm fibers. *Environ. Technol.* 1993;14(3):277-282.
- Dupont L, Bouanda J, Dummeoneal J, Applincourt M. Metal ions binding onto a Lignocellulosic substrate extracted from wheat bran: A nicadonnan approach. *Int. J. Colloid. Sci.* 2003;263:35–41.
- Villaescusa I, Martinez M, Miralles N. Heavy metal uptake from aqueous solution by cork and yohimbe bark wastes. *J. Chem. Technol. Biotechnol.* 2000;75(9):812-816.
- Wuyep PA, Chuma AG, Awodi S, Nok AJ. Biosorption of Cr, Mn, Fe, Ni, Cu, Pb metals from petroleum refinery effluent by calcium alginate immobilized mycelia of *Polyporus squamosus*. *Sc. Res. Esaaay.* 2007;2(7):217–221.
- Charamathy S, Chung W, Marshall WE. Adsorption of selected toxic metals by Modified Pea nuts shells. *J. Chem. Technol. Biotechnol.* 2001;75:791-797.
- Osemeahon SA, Esenowo DI. Evaluation on the application of immobilized konkoli (*Maesopsis eminii*) immobilized leaves for the removal of Pb, Cd and Zn in aqueous solution. *Journal of Pure and Applied Chemistry.* 2012;6(5):59-64.
- Mahvi AH. Application of agricultural fibres in pollution removal from aqueous solution. *Int J. Environ Sci Tech.* 2008;5(2):275-285.
- Rao GP, LU C, SU F. Sorption of Divalent metal ions from aqueous solution by carbon nanotubes: A review. *Separation and Purification Technology.* 2007;58:224-231
- Wu CH. Studies of the equilibrium and thermodynamics adsorption of  $Cu^{2+}$  onto produced and modified carbon nanotubes. *J. Colloid and interface Sci.* 2007;311(2):338-346.
- Naiya TK, Bhattacharya AK, Das SK. Adsorptive removal of Cd (II) ions from aqueous solutions by rice husk ash. *Environmental Progress in chemical Engineering.* 2009;28(4):535-546.
- Cieslak-Golanka M. Spectroscopy of Chromium (VI) species. *Coord. Chem. Rev.* 1991;109(2):223-249.
- Liping D, Yingying S, Hua S, Xinting W, Xidobin Z. Sorption and desorption of lead (II) from waste water by green algae *Cladophora fascicularis*. *Journal of Hazardous Materials.* 2007;143:220-225.
- Sanchez A, Balleste, A, Blazquesz, ML, Gonzalez F, Munzo J, Hamaini. A

- Biosorption of copper and zinc by *Cymodocea nodosa*. FEMS Microbiology Rev. 1990;23:(5)527-536.
19. Horsfall MJ, Spiff AI. Equilibrium sorption study of  $Al^{3+}$ ,  $Co^{2+}$  and  $Ag^+$  in aqueous solutions. By fluted pumpkin (*Telfeiria occidentalis* Hook F.) Waste Biomass. Actachim Slov. 2005;52:174-181.

© 2015 Tizhe et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:  
<http://www.sciencedomain.org/review-history.php?iid=808&id=7&aid=7145>